

## **TRASH IDENTIFICATION IN MILL LAYDOWN**

**Jonn Foulk and David McAlister**

**USDA-ARS Cotton Quality Research Station**

**Clemson, SC**

**K.B. Kulasekera**

**Department of Mathematical Science**

**Clemson University**

**Clemson, SC**

### **Abstract**

Cotton trash is known to affect textile-processing efficiency. Removal of cotton trash has often been a means to improve textile spinning. To combat trash and efficiency problems, Hamrick Mills (as do other textile mills) specifies cotton bales, which they acquire, should be no higher than a 3 leaf for processing on their Murata Airjet Spinner (MJS) or Murata Vortex Spinner (MVS). This leaf grade cut-off point is based on their past spinning experiences which point toward processing problems during weaving and excessive loom stops. This research determined how HVI Trashmeter software evaluates cotton trash and its particle size distribution in a 40-bale textile mill laydown. This study compared the distribution of particles within all bales and how similar these bales were to one another. The study further compared the change in trash particle distribution and HVI properties through the bales. Further work is needed to determine if leaf grade or trash particle distribution provide enough information for the measurement of cotton trash in high speed textile spinning.

### **Introduction**

One cotton bale contains approximately 60 billion fibers (Steadman, 1997) and unidentified levels of trash and dust particles. Since cotton is produced in the field rather than at a manufacturing facility, it is difficult to control all trash created during production. Cotton is one of the most important natural fibers and fiber testing is done almost every place where cotton is grown. Textile processing is influenced by trash components found in all cotton bales. Cottons and their trash components are diverse in nature and respond differently to textile cleaning and further processing. The type and amount of trash, fiber-to-trash adhesion, and how well its behavior mimics a fiber determines the ease of trash removal.

Standardized testing was developed for cotton trash measurement because trash affects further processing and utilization. Historically, cotton fiber measurements were first performed by humans specially trained to differentiate fibers based on their length, strength, fineness, color, and trash (Shofner and Shofner, 2000). Today, the United States Department of Agriculture (USDA) Agricultural Marketing Service (AMS) classes and grades cotton for a small fee (Agricultural Marketing Service, 1993). These cotton fiber measurements have progressed from a subjective human classer to the objective High Volume Instrument (HVI). The cotton trash measurement (percentage of surface area) of non-lint materials obtained using a scanning video camera mounted within the HVI. This percentage of non-lint surface area is correlated to the classer's leaf grade (1 through 7 and a 'below grade'), which is a visual estimate of cotton plant leaf particles in cotton.

Cotton contains troublesome trash with conflicting issues such as leaf vs. seed coat, size vs. type, and size vs. distribution. These conflicting issues are confounded because trash particles can be difficult to locate, measure, and describe since trash can arise from many components and can be irregularly sized, erratically positioned, partly covered by cotton fibers, or light colored in nature. These trash particles originate either from the cotton plant with various parts of the leaf, stem, bark, seed, and hull or from the local environment including grass, sand, dust and other contamination. Cotton contamination including large trash and small pepper trash is commonly referred to as visible foreign matter. Individuals commonly refer to pepper trash as having a size around 0.02 in, while seed coat fragment typically range from 0.017 - 0.025 in. Respirable dust is commonly referred to fall between 0-15  $\mu$  (0-0.0006 in), micro-dust 15-50  $\mu$  (0-0.002 in), dust <500  $\mu$  (<0.02 in), and trash >500  $\mu$  (>0.02 in) (H. Ghorashi, personal communication, 2000).

The HVI provides a rapid trash measurement at a low cost using a video camera at one set of conditions. Recent HVI software developments are able to rapidly quantify cotton trash and provide a particle frequency distribution (Ghorashi, 2000). As processing speeds increase, continued improvements in measuring cotton are desirable. New techniques or instruments are necessary to provide rapid, consistent, quantitative, and additional fiber property results with confirmed reliability. The goal is to determine the total degree of fiber contamination and understand how each fraction impacts textile processing.

## **Materials and Methods**

### **Cotton**

Sample bales were all harvested, ginned, and baled by commercial methods and selected by Hamrick Mills because of their narrow range of leaf grade officially determined by USDA AMS. To combat trash and efficiency problems, Hamrick Mills specifies cotton bales that they purchase should be no higher than a 3 leaf for processing on their Murata Airjet Spinner (MJS) or Murata Vortex Spinner (MVS). This is based on their past efforts where they experience processing problems during weaving with excessive loom stops. The fiber properties (see Table 1 for official classification) used for selection of all cotton bales were determined by High Volume Instrumentation (HVI). The HVI allows cotton fibers to be tested for length, strength, fineness, color and trash according to established standards (ASTM, 1993).

### **Cotton Testing**

To evaluate the new and improved HVI Trashmeter, cotton quality trash measurements were performed on a HVI 900A (Zellweger Uster, Knoxville, TN) by the Testing Laboratory at Cotton Quality Research Station (CQRS). The viewing area of the HVI is 9 in<sup>2</sup> with one square inch approximately equal to 14,363 pixels. The HVI Trashmeter camera has a sensing array of 510 by 480 pixels with a resolution of 484 by 464 pixels with every other line used. The Trashmeter ignores trash particles less than 2 pixels in area for noise reduction with the software calculating the total trash, percent of viewed area, and trash particle distribution. The smallest viewable trash accepted by this software is 0.013 inch. The Trashmeter allows cotton to be evaluated for the number of trash particles per various classes of trash size, distribution of trash particles, average particle size, and sum of trash particles. Fiber properties (see Tables 2 - 4 for USDA, ARS, CQRS HVI results) for all cotton bales were determined by High Volume Instrumentation (HVI). Trash particle size distributions were obtained for all cotton samples.

### **Textile Processing**

A forty-bale laydown was analyzed from the Hamrick Mills Musgrove plant in Gaffney, South Carolina. This laydown contained cotton purchased according to their specifications (no greater than a 3 leaf grade). Initially, four samples were removed from the surface of all bales for HVI Trashmeter testing. Two hours later a 100 lb mat of cotton was removed from all bales with four samples per bale later removed from the mat's interior. Lastly after two hours another four samples were removed from the surface of the 40-bale laydown for HVI Trashmeter testing. A second set of official HVI fiber properties were determined on cotton samples removed after two h.

Cotton from the 40-bale laydown was removed for processing using a Truetzschler BDT 019 Top Feeder. All cotton was processed through the following sequence: Truetzschler LVSA condenser fan, Truetzschler MPM10 (ten cell mixer), Truetzschler Maxi-Flo, Truetzschler CVT1, Truetzschler Dustek, Truetzschler condenser fan, Truetzschler MPM4 mixer (4 cell mixer), Truetzschler MS reserve, Truetzschler 803 card. Cotton was processed through the card to produce a 60-grain sliver at 140 lbs/hour. Discharge point on Truetzschler MPM10 where blending first occurs and cotton sliver were cotton collection points for additional HVI Trashmeter testing.

The HVI classification properties and mean Trashmeter data were statistically analyzed with the MEANS procedure in SAS to compute descriptive statistics for variables across all observations (SAS Institute Inc., 1985).

## **Results and Discussion**

Counting and sizing cotton trash by hand would be a very tedious, time-consuming, and subjective process. Preliminary work with uniformly located trash shows that asymmetrical trash diverse in origin and color can be easily measured with the new Trashmeter software (Fouk et al., 2003). Results indicate that with new software the HVI 900A Trashmeter is able to estimate the size of each particle counted consequently creating a trash frequency distribution (Fouk et al., 2003). This preliminary work led to the use of this Trashmeter software with a known multi-bale laydown of narrow leaf grade. Trash classification was performed using the new HVI Trashmeter software and referred to as 1 (<5 pixels), 2 (>5<10 pixels), 3 (>10<15 pixels), in 5 pixel increments until category 21 (>100<200 pixels), 22 (>200<300 pixels), 23 (>300<400 pixels), 24 (>400<500 pixels), and 25 (>500 pixels). Generated trash classification results were compiled for all bales during each sampling period. These data results demonstrated an exponential decay of trash particles with many small particles decreasing to a few large particles (see Figures 1-3).

Aware that trash particle size distributions were exponential, LIFEREG a standard SAS procedure for parametric survival analysis was used for bale assessment (SAS Institute Inc., 1985). Raw trash particle sizes, rather than trash classification results, within each bale in the laydown were compared using SAS LIFEREG. SAS LIFEREG is a procedure that fits parametric models to the trash particle size data and conducts a statistical test to determine whether the distributions are the same. Trash particle size distribution data were fitted to a Weibull model using Weibull regression. Cotton bales were the independent variable and trash particle size was the dependent variable. Analysis of raw trash histogram data (visibly the shape of survival data) involves two main functions that are inter-related: the hazard function and the survival function (Kleinbaum,

1997). The hazard function  $h(t)$  provides the instantaneous potential of an individual to undergo the event of interest given survival until time  $t$  (determines the shape of the distribution). The survival function  $S(t)$  gives the probability of survival for longer than time  $t$  (overall survival time). There exists a mathematical relationship between these two functions because a high probability of survival corresponds to a low probability of undergoing the event of interest (Kleinbaum, 1997).

Results generated from LIFEREG determine equation coefficients and p-values for each bale. The p-values indicate which bales are different than the remainder of the bales that form the equation's baseline. Evaluating the laydown with the new Trashmeter software at time zero, demonstrated that bales 2, 6, 9, 10, 12, 14, 16, 24, 27, 30, 32, 36, and 38 were significantly different ( $P < 0.05$  level) while at the ( $P < 0.10$  level) bales 3, 7, 20, 29, 31, and 37 were significantly different. Evaluating the laydown with the new Trashmeter software after 2 h, demonstrated that bales 2, 3, 7, 9, 16, 17, 19, 22, 23, 28, 29, 32, 33, 38, 39, and 40, were significantly different ( $P < 0.05$  level) while at the ( $P < 0.10$  level) bales 14, 15, and 26 were significantly different. Evaluating the laydown with the new Trashmeter software after 4 h, demonstrated that bales 2, 3, 7, 8, 9, 14, 16, 17, 27, and 38 were significantly different ( $P < 0.05$  level) while at the ( $P < 0.10$  level) bales 12, 29, 32, and 37 were significantly different. Within this 40-bale laydown, bales 2, 3, 7, 9, 14, 16, 29, 32, and 38 consistently appear to be different than the other bales. These results appear to demonstrate that there is a significant difference in trash particle size distributions between the 40 cotton bales. All cotton bales were marketed to have an official leaf grade of 3. These results demonstrate that this leaf grade appears to cover a range of particle size distributions. Further evaluation of the 40-bale laydown over time demonstrated that there was no significant particle distribution difference ( $P < 0.05$  level) between sampling periods.

Summarizing the official HVI trash percent area and classer leaf properties demonstrated that the 40 bale laydown had a mean trash area of 0.35 % with a standard deviation 0.09 and a coefficient of variation of 24.72 (Table 5). Classer leaf had a leaf grade of 3.16 and a standard deviation of 0.54 and coefficient of variation of 17.02. Cotton quality properties measured at CQRS on a HVI produced comparable results (Table 6). The mean trash percent area was 0.35 % with a standard deviation of 0.10 and coefficient of variation of 28.92. HVI leaf at CQRS had a mean grade of 3.03 with a standard deviation of 0.59 and coefficient of variation of 19.55. Trashmeter software demonstrated that the mean size of trash in the laydown was 0.048 in which compared favorably with the mean size of the mixed cotton (0.047 in) removed from the discharge point on the Truetzschler MPM10 (Table 7). As expected for cleaned and carded cotton, card sliver trash was much smaller with a mean size of 0.016 in.

Bales of known and constant leaf grade appear to have different trash particle size distributions. Differences in trash particle size distributions exist between bales but they do not appear to vary with time. These different trash particle size distributions may be able to provide additional information beyond leaf grade. These preliminary results may allow textile mills to better understand the type of trash distributions causing processing problems. In other words, more trash particle distribution information may help explain the impact of trash on high speed processing.

### **Disclaimer**

Mention of a trade name, proprietary product, or specific equipment does not constitute a guarantee or warranty by the U.S. Department of Agriculture, information is for information purposes only, and does not imply approval of a product to the exclusion of others that may be suitable.

### **References**

- Agricultural Marketing Service. 1993. The classification of cotton. Agricultural Handbook 566. Agricultural Marketing Service, USDA ARS, Washington, DC. 24 pp.
- Fouk, J., McAlister, D., Himmelsbach, D., and Hughs, E. 2003. Small trash identification in cotton. Proceedings - Beltwide Cotton Conf. Nashville, TN, 6-10 Jan., Natl. Cotton Counc. Am., Memphis, TN., 10 p. <http://www.cotton.org/beltwide/>
- Kleinbaum, D. 1997. Survival Analysis – A Self-Learning Text. Springer-Verlag. NY, NY. 324 pp.
- SAS Institute Inc., 1985. SAS® User's Guide: Statistics, version 5 edition. SAS Institute Inc., Cary, NC, 956 pp.
- Shofner, F., and Shofner, K. 2000. Cotton classing in the new millennium. 25<sup>th</sup> International Cotton Conference Bremen. March 1-4, 2000. Bremen, Germany.
- Steadman, R. 1997. Cotton testing. Textile Progress. 27(1):1-65.

Table 1. Official cotton bale classification data\*

<b>Bale</b>	<b>Mic</b>	<b>Strength (g/tex)</b>	<b>Reflectance (Rd)</b>	<b>Yellowness (+b)</b>	<b>Trash (%)</b>	<b>UHM (in)</b>	<b>UF (%)</b>	<b>Leaf</b>	<b>Grade color</b>	<b>Quad color</b>
1	4.0	29.7	76	8.5	0.3	1.12	82	3	31	2
2	4.6	34.5	77	7.1	0.4	1.14	83	3	41	1
3	4.6	34.6	74	8.2	0.3	1.14	82	3	41	1
4	3.9	29.1	74	8.2	0.4	1.12	82	3	41	1
5	4.4	30.2	76	8.6	0.2	1.12	83	3	31	2
6	4.0	31.2	76	6.5	0.3	1.18	81	3	41	2
7	4.1	29.9	77	8.9	0.4	1.13	83	3	31	1
8	4.6	34.8	76	7.4	0.4	1.14	83	3	41	1
9	4.3	31.0	76	8.6	0.3	1.13	83	3	31	2
10	4.4	30.8	75	8.3	0.4	1.12	83	3	41	1
11	4.0	31.1	76	8.9	0.3	1.12	82	3	31	3
12	4.2	29.9	77	7.6	0.3	1.15	83	3	41	1
13	4.5	30.3	76	6.8	0.2	1.12	82	3	41	1
14	4.9	30.0	78	7.6	0.3	1.12	81	3	31	2
15	4.6	34.7	75	7.4	0.5	1.15	83	3	41	1
16	4.0	29.8	76	8.0	0.4	1.13	82	3	41	1
17	4.2	30.5	76	8.7	0.4	1.15	82	3	31	2
18	4.6	32.0	77	7.8	0.3	1.13	81	3	31	2
19	4.9	30.2	77	7.7	0.2	1.13	81	3	31	2
20	3.8	30.0	75	8.6	0.4	1.14	84	3	31	4
21	4.0	31.0	76	6.1	0.3	1.15	82	3	41	2
22	4.1	30.6	75	8.7	0.3	1.14	83	3	31	4
23	4.6	34.8	76	7.6	0.4	1.14	83	3	41	1
24	4.1	29.8	76	8.6	0.2	1.12	82	3	31	2
25	4.3	30.3	74	8.1	0.4	1.13	84	3	41	1
26	4.0	29.9	75	8.1	0.5	1.13	82	3	41	1
27	4.2	30.0	75	9.2	0.5	1.14	83	3	31	3
28	4.5	31.8	74	8.0	0.2	1.13	83	3	41	1
29	4.8	30.9	77	7.7	0.2	1.12	82	3	31	2
30	3.8	31.5	75	6.3	0.3	1.14	82	3	41	2
31	3.8	29.6	77	8.5	0.3	1.14	83	3	31	1
32	4.6	35.0	76	7.3	0.4	1.15	83	3	41	1
33	4.6	34.8	76	7.4	0.5	1.14	83	3	41	1
34	4.2	29.9	76	8.9	0.3	1.12	83	3	31	3
35	4.4	30.0	75	8.6	0.3	1.12	82	3	31	4
36	3.8	32.5	75	6.2	0.3	1.17	83	3	41	2
37	4.1	30.7	77	8.6	0.3	1.13	83	3	31	1
38	4.4	31.0	76	8.2	0.2	1.12	83	3	31	2
39	4.7	29.5	77	6.4	0.3	1.16	82	3	41	1
40	3.7	30.3	75	8.0	0.4	1.13	82	3	41	1

\* USDA, ARS, AMS, Memphis, TN.

Table 2. HVI cotton bale classification data at time zero\*

<b>Bale</b>	<b>Mic</b>	<b>Strength (g/tex)</b>	<b>Reflectance (Rd)</b>	<b>Yellowness (+b)</b>	<b>Trash (%)</b>	<b>UHM (in)</b>	<b>UF (%)</b>	<b>Leaf</b>	<b>Grade color</b>	<b>Quad color</b>
1	3.92	26.4	75.8	8.9	0.49	1.119	82.2	3	31	3
2	4.52	32.8	75.2	8.0	0.25	1.139	82.9	2	41	1
3	4.65	32.7	76.1	8.7	0.55	1.142	82.5	3	31	2
4	4.59	31.8	76.6	7.7	0.34	1.139	82.1	3	41	1
5	4.41	28.5	75.0	8.9	0.34	1.098	83.2	3	31	4
6	3.90	32.6	74.5	6.6	0.37	1.178	83.0	3	41	2
7	4.17	28.8	75.3	8.9	0.31	1.130	82.8	3	31	4
8	4.58	32.7	73.5	8.0	0.49	1.130	82.4	3	41	1
9	4.31	29.5	74.7	8.4	0.57	1.145	83.3	3	41	1
10	4.51	32.4	74.3	7.8	0.46	1.140	83.3	3	41	1
11	4.65	28.5	75.5	9.1	0.31	1.106	84.1	3	31	3
12	4.82	30.2	76.6	8.3	0.25	1.130	81.4	2	31	2
13	4.34	26.2	74.5	6.8	0.21	1.082	81.8	2	41	2
14	4.57	34.9	74.1	7.4	0.52	1.144	84.0	3	41	2
15	3.97	27.8	74.0	8.4	0.33	1.116	82.0	3	41	1
16	3.77	28.6	72.7	8.6	0.34	1.131	81.1	3	41	3
17	4.19	29.8	74.6	8.9	0.34	1.134	83.5	3	31	4
18	4.22	30.9	74.8	9.1	0.50	1.130	83.6	3	31	4
19	4.01	32.0	75.3	6.2	0.37	1.159	81.8	3	41	2
20	4.48	28.7	74.4	9.0	0.28	1.142	83.2	3	31	4
21	4.11	28.3	75.3	8.7	0.30	1.108	82.2	3	31	4
22	4.52	33.4	74.0	8.0	0.46	1.144	83.9	3	41	1
23	4.49	28.8	75.0	8.2	0.37	1.135	83.9	3	41	1
24	4.14	28.9	75.4	8.9	0.33	1.115	82.7	3	31	4
25	3.98	28.0	73.4	8.5	0.56	1.125	81.6	3	41	3
26	4.27	29.0	74.9	9.4	0.31	1.133	83.1	3	31	3
27	4.76	33.0	76.1	7.6	0.23	1.124	81.8	3	41	1
28	4.86	30.5	75.5	8.3	0.33	1.120	81.4	3	31	2
29	3.92	31.1	75.2	6.8	0.37	1.158	82.8	3	41	2
30	4.53	34.2	74.8	7.6	0.62	1.146	83.3	3	41	1
31	3.99	28.3	76.8	8.9	0.34	1.134	83.3	3	31	1
32	4.52	33.1	74.0	8.0	0.51	1.156	83.8	3	41	1
33	4.58	33.0	73.6	8.1	0.46	1.145	83.3	3	41	1
34	4.26	28.3	74.4	9.4	0.33	1.109	82.9	3	32	2
35	4.45	29.0	74.7	8.9	0.43	1.143	84.4	3	31	4
36	3.85	33.4	74.5	6.2	0.38	1.197	83.5	3	41	2
37	4.01	29.5	75.6	8.6	0.38	1.140	84.3	3	31	2
38	4.44	28.6	76.2	8.5	0.20	1.094	82.5	2	31	2
39	4.63	27.2	77.0	6.8	0.47	1.133	82.7	3	41	1
40	3.66	28.9	73.0	8.4	0.37	1.136	82.5	3	41	3

\* USDA, ARS, CQRS, Clemson, SC.

Table 3. HVI cotton bale classification data after 2 h\*

<b>Bale</b>	<b>Mic</b>	<b>Strength (g/tex)</b>	<b>Reflectance (Rd)</b>	<b>Yellowness (+b)</b>	<b>Trash (%)</b>	<b>UHM (in)</b>	<b>UF (%)</b>	<b>Leaf</b>	<b>Grade color</b>	<b>Quad color</b>
1	3.96	25.8	74.9	8.7	0.56	1.109	81.6	3	31	4
2	4.58	33.4	74.0	8.0	0.46	1.166	82.9	3	41	1
3	4.51	29.5	75.7	9.1	0.56	1.163	83.1	3	31	3
4	3.74	28.4	72.7	8.8	0.46	1.137	81.9	3	41	3
5	4.43	28.3	74.5	8.8	0.36	1.111	82.8	3	31	4
6	3.95	31.1	74.5	6.7	0.51	1.163	83.0	3	41	2
7	4.18	28.3	75.2	8.8	0.31	1.145	82.6	3	31	4
8	4.57	30.6	73.2	8.0	0.62	1.155	83.0	3	41	2
9	4.27	29.6	75.6	8.7	0.43	1.133	83.1	3	31	2
10	4.61	28.2	76.1	9.3	0.23	1.115	83.3	2	31	3
11	4.04	29.3	74.4	8.9	0.37	1.118	82.4	3	41	3
12	3.84	29.2	76.6	8.4	0.36	1.143	82.2	2	31	2
13	4.37	27.3	74.4	7.2	0.40	1.111	82.5	2	41	2
14	4.84	30.9	76.5	8.2	0.31	1.124	81.6	3	31	2
15	4.68	33.6	74.1	7.7	0.56	1.153	83.9	3	41	2
16	3.93	28.1	74.0	8.8	0.34	1.139	81.9	3	41	3
17	4.22	30.7	75.0	9.1	0.33	1.142	83.4	3	31	4
18	4.64	27.8	76.6	7.9	0.21	1.124	82.6	2	31	2
19	4.89	31.5	75.4	8.4	0.31	1.132	82.8	3	41	1
20	3.94	33.3	73.6	9.3	0.40	1.144	81.4	3	32	2
21	3.98	33.7	74.7	6.5	0.41	1.139	82.6	3	41	2
22	4.16	28.2	74.9	9.1	0.36	1.130	82.8	3	31	4
23	4.74	31.4	73.8	7.9	0.46	1.134	83.2	3	41	1
24	4.06	28.3	75.3	9.2	0.25	1.133	82.9	3	31	4
25	4.35	28.5	75.0	8.4	0.40	1.134	84.1	3	41	1
26	3.91	26.9	73.8	8.3	0.37	1.061	81.7	3	41	1
27	4.31	26.5	74.8	9.3	0.28	1.075	81.8	3	31	3
28	4.43	26.4	74.8	8.4	0.31	1.104	81.3	3	41	1
29	4.79	31.4	76.1	7.8	0.28	1.124	82.7	3	41	1
30	3.83	30.5	74.9	6.5	0.44	1.156	81.8	3	41	2
31	3.80	28.7	76.1	9.2	0.31	1.136	83.3	3	31	3
32	4.53	32.9	74.8	8.1	0.49	1.148	82.8	3	41	1
33	4.62	33.2	73.9	8.3	0.55	1.144	83.5	3	41	1
34	4.28	28.8	74.5	9.2	0.31	1.104	82.9	3	31	4
35	4.49	30.5	73.7	9.1	0.33	1.122	82.3	3	31	4
36	4.03	34.5	74.4	6.5	0.46	1.161	82.5	3	51	1
37	4.09	28.7	75.7	8.8	0.23	1.141	83.1	2	31	3
38	4.38	28.4	75.4	8.8	0.27	1.108	81.5	3	31	4
39	4.67	27.8	77.3	7.0	0.33	1.125	82.0	2	41	1
40	3.75	28.2	73.1	8.7	0.56	1.141	81.6	3	41	3

\* USDA, ARS, CQRS, Clemson, SC.

Table 4. HVI cotton bale classification data after 4 h\*

<b>Bale</b>	<b>Mic</b>	<b>Strength (g/tex)</b>	<b>Reflectance (Rd)</b>	<b>Yellowness (+b)</b>	<b>Trash (%)</b>	<b>UHM (in)</b>	<b>UF (%)</b>	<b>Leaf</b>	<b>Grade color</b>	<b>Quad color</b>
1	4.0	26.6	77	8.6	0.28	1.15	82.8	3	31	1
2	4.6	36.0	76	8.4	0.24	1.16	84.6	4	31	2
3	4.6	33.2	81	8.2	0.26	1.15	83.5	4	21	1
4	3.7	29.5	75	8.2	0.36	1.13	82.3	3	41	1
5	4.4	29.2	77	8.8	0.27	1.12	83.6	2	31	1
6	3.9	33.0	77	6.2	0.37	1.21	83.7	4	41	2
7	4.2	29.3	78	8.8	0.29	1.14	83.8	3	31	1
8	4.6	33.8	76	7.7	0.30	1.13	84.0	5	41	1
9	4.3	31.6	75	8.5	0.46	1.15	84.5	5	41	1
10	4.7	28.7	79	9.1	0.28	1.13	83.3	3	21	1
11	4.0	29.9	80	8.5	0.24	1.12	84.2	2	21	1
12	4.0	29.9	80	7.9	0.26	1.15	84.3	3	31	1
13	4.5	27.4	75	6.9	0.24	1.12	82.7	3	41	2
14	4.9	30.9	79	8.0	0.26	1.14	82.9	3	31	1
15	4.7	35.4	75	7.8	0.32	1.16	84.7	4	41	1
16	3.8	29.7	78	8.0	0.32	1.14	82.8	4	31	1
17	4.3	31.1	79	8.9	0.28	1.16	84.8	4	21	2
18	4.7	34.7	77	7.5	0.24	1.15	82.4	3	41	1
19	4.9	31.5	79	7.9	0.31	1.15	82.9	3	31	1
20	3.9	30.4	77	8.7	0.34	1.16	84.1	4	31	1
21	4.0	33.0	76	6.5	0.32	1.19	84.1	4	41	2
22	4.0	30.2	76	8.6	0.27	1.13	84.0	2	31	2
23	4.6	34.0	74	7.7	0.24	1.14	84.5	4	41	1
24	4.1	29.3	76	8.8	0.35	1.13	83.8	3	31	3
25	4.4	31.7	75	8.3	0.24	1.15	84.6	4	41	1
26	4.3	29.5	76	9.0	0.30	1.14	84.4	4	31	3
27	4.2	29.4	77	9.0	0.29	1.15	83.7	3	31	3
28	4.4	26.6	77	8.4	0.22	1.10	81.1	3	31	2
29	4.9	32.9	81	7.4	0.20	1.15	82.5	2	31	1
30	3.8	33.3	77	6.2	0.28	1.18	83.5	2	41	2
31	3.8	29.9	79	8.5	0.30	1.14	84.0	4	21	2
32	4.6	34.5	79	7.5	0.32	1.15	83.5	5	31	1
33	4.7	35.0	77	7.7	0.26	1.14	83.8	4	41	1
34	4.3	28.9	75	9.0	0.23	1.10	84.0	3	31	4
35	4.5	29.3	78	8.5	0.29	1.15	84.9	3	31	1
36	3.9	33.3	77	6.0	0.32	1.19	84.8	3	41	2
37	3.9	30.4	76	8.7	0.20	1.16	84.5	2	31	2
38	4.5	28.4	78	8.4	0.28	1.11	82.8	3	31	1
39	4.8	28.5	78	7.0	0.24	1.14	84.1	3	41	1
40	3.7	28.1	74	8.5	0.35	1.13	82.8	4	41	3

\* USDA, ARS, CQRS, Clemson, SC.

Table 5. Summary of Official HVI cotton properties of 40 bale laydown \*

	<b>Mic</b>	<b>Strength (g/tex)</b>	<b>Reflect. (Rd)</b>	<b>Yellowness (+b)</b>	<b>Trash (%)</b>	<b>UHM (in)</b>	<b>UF (%)</b>	<b>Classer Leaf</b>	<b>Color grade</b>	<b>Color quadrant</b>
Mean	4.36	30.17	75.49	8.00	0.35	1.13	82.54	3.16	36.38	1.96
Standard deviation	0.32	2.01	1.04	0.84	0.09	0.016	0.71	0.54	5.02	1.00
Coefficient of variation	7.44	6.68	1.38	10.43	24.72	1.44	0.86	17.02	13.79	50.92

\* Official HVI properties obtained at USDA, AMS, Memphis, TN from 2 separate locations within bales.

Table 6. Summary of CQRS HVI cotton properties of 40 bale laydown \*

	Mic	Strength (g/tex)	Reflect. (Rd)	Yellowness (+b)	Trash (%)	UHM (in)	UF (%)	HVI Leaf	Color grade	Color quadrant
Mean	4.30	30.31	75.64	8.20	0.35	1.14	83.03	3.03	35.52	2.05
Standard deviation	0.33	2.38	1.71	0.83	0.10	0.02	0.93	0.59	5.91	1.08
Coefficient of variation	7.77	7.86	2.25	10.18	28.92	1.99	1.12	19.55	16.64	52.85

\* HVI properties obtained at USDA, ARS, CQRS, Clemson, SC from 3 separate locations within bales.

Table 7. Summary of HVI Trashmeter 40 bale laydown \*

	40 bale Mean size (in)	40 bale Sum area (in <sup>2</sup> )	Mix Mean size (in)	Mix Sum area (in <sup>2</sup> )	Card sliver Mean size (in)	Card sliver Sum area (in <sup>2</sup> )
Mean	0.048	0.052	0.047	0.052	0.016	0.0016
Standard deviation	0.021	0.013	0.020	0.013	0.011	0.00087
Coefficient of variation	42.81	26.02	43.16	24.56	69.55	54.17

\* HVI Trashmeter results obtained at USDA, ARS, CQRS, Clemson, SC.

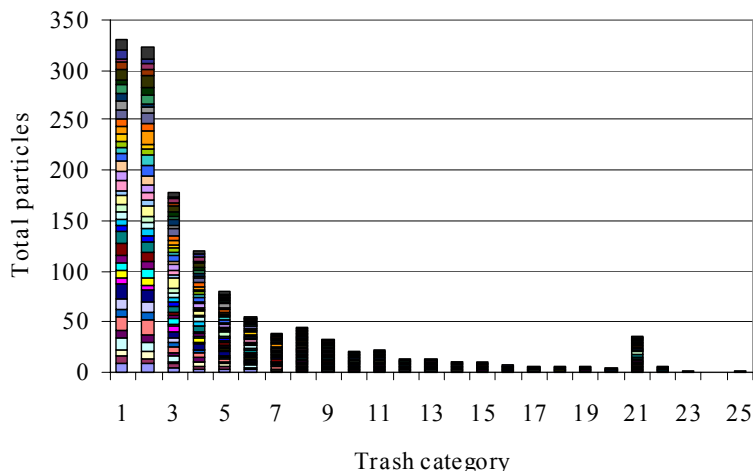


Figure 1. Exponential decay for all 40 bales illustrated with total number of particles in each trash category at time zero.

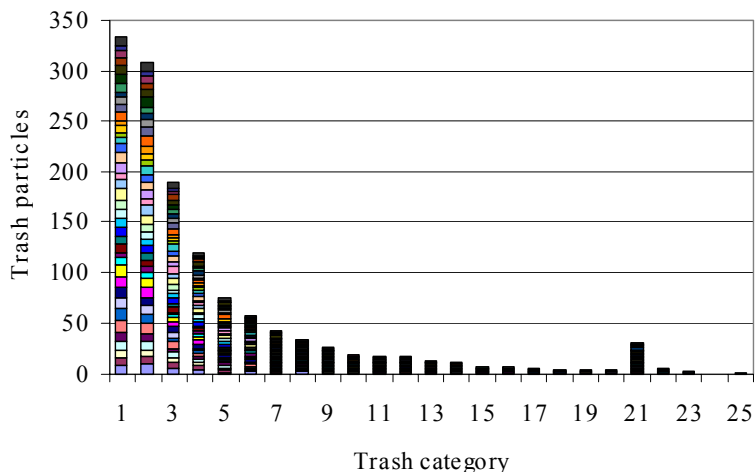


Figure 2. Exponential decay for all 40 bales illustrated with total number of particles in each trash category after 2h.



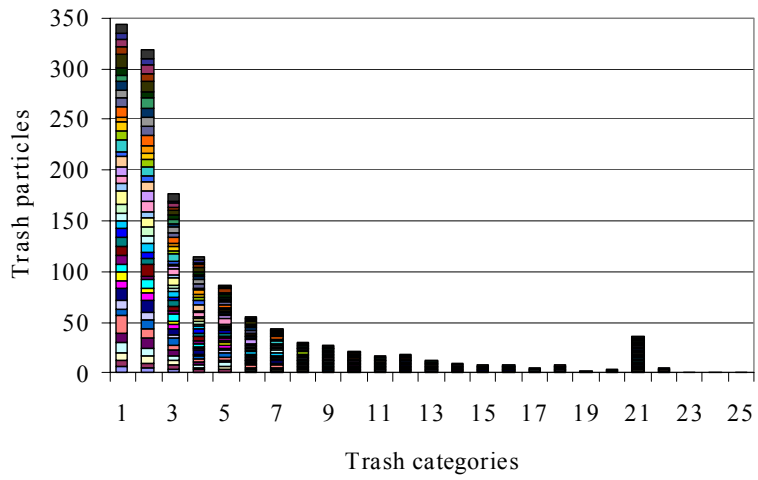


Figure 3. Exponential decay for all 40 bales illustrated with total number of particles in each trash category after 4h.